

Calcium Carbonate Storage in Amorphous Form and Its Template-Induced Crystallization[†]

T. Yong-Jin Han^{*‡} and Joanna Aizenberg^{*§}

Chemistry and Materials Science Directorate, Chemistry and Chemical Engineering Division, Lawrence Livermore National Laboratory, Livermore, California 94551, and School of Engineering and Applied Sciences, Department of Chemistry and Chemical Biology, Harvard University, 29 Oxford Street, Cambridge, Massachusetts 02138

Received July 26, 2007. Revised Manuscript Received October 12, 2007

Calcium carbonate crystallization in organisms often occurs through the transformation from the amorphous precursor. It is believed that the amorphous phase could be temporarily stabilized and stored, until its templated transition to the crystalline form is induced. Here we develop a bioinspired crystallization strategy that is based on the above mechanism. Amorphous calcium carbonate (ACC) spherulitic particles are induced to form on a self-assembled monolayer (SAM) of hydroxyl-terminated alkanethiols on a gold surface. The ACC can then be stored in a dry atmosphere as a reservoir for ions and be induced to crystallize on command by the introduction of water and a secondary surface that is functionalized with carboxylic acid-terminated SAM. This secondary surface acts as a template for oriented and patterned nucleation. Various oriented crystalline arrays and micropatterned films are formed. We also show that the ACC phase can be doped with foreign ions (e.g., magnesium) and organic molecules (e.g., dyes) and that these dopants later function as growth modifiers of calcite crystals and become incorporated into the crystals during the transformation process of ACC to calcite. We believe that our strategy opens the way to using a stabilized amorphous phase as a versatile reservoir system that can be converted in a highly controlled fashion to a crystalline form upon contacting a specially designed nucleating template in water.

Introduction

The advancements in technology and science are often fueled by the development of new materials and by the discoveries of novel properties of existing materials, which can arise from the variations of their sizes, shapes, orientation, patterns, and morphologies. This is especially true in the emerging field of nanotechnology, where the shapes, sizes, and orientation of materials are of critical importance and crucial in determining their function. In an effort to control various parameters of inorganic materials synthesis, it is particularly fruitful to study how inorganic materials are formed in nature. Biology provides numerous examples of exquisite inorganic structures with functions including magnetic, optical, and mechanical.¹ Understanding the sophisticated, precise mechanisms with which biological molecules govern the synthesis of inorganic materials in a bottom-up fashion can directly impact the nascent field of nanotechnology, where the controlled formation of materials is one of the essential components for its progress.

One example of biogenic inorganic materials with diverse micro/nanostructures and unique properties is calcium carbonate, the most abundant biomineral. The two major polymorphs of calcium carbonate, calcite and

aragonite, have traditionally garnered the most attention.^{2,3} Recently, we have shown that amorphous calcium carbonate (ACC) might have multiple functions and importance in the biomineralization process.^{4,5} A number of studies addressing the structure^{6,7} and function of biogenic ACC followed.^{8,9} It has been demonstrated that a metastable ACC phase is often a transient precursor to the two dominant polymorphs, calcite^{10,11} and aragonite.¹² Stable ACC is also formed by organisms and used as a skeletal material.^{4,13} It has been proposed that ACC might participate in developing the final intricate microstructures of the biogenic crystalline calcium carbonates.^{14,15}

- (2) Addadi, L.; Weiner, S. *Angew. Chem., Int. Ed.* **1992**, *31*, 153.
- (3) Davis, K. J.; Dove, P. M.; De Yoreo, J. J. *Science* **2000**, *290*, 1134.
- (4) Aizenberg, J.; Addadi, L.; Weiner, S.; Lambert, G. *Adv. Mater.* **1996**, *8*, 222.
- (5) Beniash, E.; Aizenberg, J.; Addadi, L.; Weiner, S. *Proc. R. Soc. London B* **1997**, *264*, 461.
- (6) Hasse, B.; Ehrenberg, H.; Marxen, J. C.; Becker, W.; Epple, M. *Chem.—Eur. J.* **2000**, *6*, 3679.
- (7) Levi-Kalishman, Y.; Raz, S.; Weiner, S.; Addadi, L.; Sagi, I. *Adv. Funct. Mater.* **2002**, *12*, 43.
- (8) Addadi, L.; Raz, S.; Weiner, S. *Adv. Mater.* **2003**, *15*, 959.
- (9) Meldrum, F. C. *Int. Mater. Rev.* **2003**, *48*, 187.
- (10) Beniash, E.; Addadi, L.; Weiner, S. *J. Struct. Biol.* **1999**, *125*, 50.
- (11) Politi, Y.; Levi-Kalishman, Y.; Raz, S.; Wilt, F.; Addadi, L.; Weiner, S.; Sagi, I. *Adv. Funct. Mater.* **2006**, *16*, 1289.
- (12) Weiss, I. M.; Tuross, N.; Addadi, L.; Weiner, S. *J. Exp. Zool., Part B* **2002**, *293*, 478.
- (13) Aizenberg, J.; Lambert, G.; Weiner, S.; Addadi, L. *J. Am. Chem. Soc.* **2002**, *124*, 32.
- (14) Aizenberg, J.; Muller, D. A.; Grazul, J. L.; Hamann, D. R. *Science* **2003**, *299*, 1205.
- (15) Politi, Y.; Arad, T.; Klein, E.; Weiner, S.; Addadi, L. *Science* **2004**, *306*, 1161.

[†] Part of the “Templated Materials Special Issue”.

^{*} Corresponding authors. E-mail: han5@llnl.gov (T.Y.-J.H.), jaizenberg@seas.harvard.edu (J.A.).

[‡] Lawrence Livermore National Laboratory.

[§] Harvard University.

(1) Lowenstam, H. A.; Weiner, S. *On Biomineralization*; Oxford University Press: Oxford, U.K., 1989.

The formation of synthetic spherulitic ACC stabilized by magnesium ions that acted as a transient precursor to a crystalline form of calcite was observed by Reddy and Nancollas in 1976.¹⁶ Since then, numerous studies of the synthesis of ACC in the metastable form and its subsequent conversion to crystalline calcium carbonates have been reported.^{17–22} The stabilization of ACC was commonly achieved by using various solution additives, including magnesium,^{17,23,24} biological macromolecules,^{4,13} and synthetic polymers.^{25–27} In particular, we have shown that hydroxyamino acid-rich macromolecules extracted from biogenic stable ACC induce the formation of a stable synthetic ACC phase.^{4,13} The formation of peptide-stabilized ACC that acts as a “liquid precursor phase” was reported by Gower.^{28–30} We have also shown that ACC can be surface-stabilized in the absence of additives when the precipitation of calcium carbonate occurs on a self-assembled monolayer (SAM) functionalized with biologically relevant hydroxyl and phosphate groups.¹⁴ By introducing a three-dimensional (3D) micropatterned environment and a single nucleation site on such a template, we have achieved the conversion of the ACC phase into a large, oriented, micropatterned single calcite crystal. Interesting examples of single micropatterned calcite crystals formed as a result of the amorphous-to-crystalline transition within a 3D template were reported by Meldrum et al.^{9,31,32}

These studies have clearly shown that the ability to control the transition from an amorphous to a crystalline form emerges as a powerful biomimetic synthetic strategy that allows the fabrication of oriented and arbitrarily micropatterned crystalline materials. The difficulty arises from the high solubility of ACC and its spontaneous, uncontrolled recrystallization.³³ Successful synthesis of stable ACC with or without additives will make it possible to store the material, manipulate the particles, study their structure, explore the transformation process, and possibly understand its role in biomineralization. The function of amorphous phases as a storage for ions is believed to be a general

biomineralization strategy.¹ Here we describe a facile synthesis of ACC on a SAM template functionalized with hydroxyl groups. We show that ACC can be successfully stored in a dry atmosphere, and the highly controlled crystallization can be triggered when needed by contacting a secondary template that bears calcite nucleating sites in a humid environment or aqueous solution.

Experimental Section

Templates. Gold surfaces were prepared by E-beam evaporation of 50 nm Au onto Si(100) wafers primed with 2 nm Ti as an adhesion promoter. Substrates were immediately submerged into a 5 mM solution of a corresponding thiol in ethanol [for hydroxyl-terminated surfaces, HS(CH₂)₁₁OH was used; for carboxylic acid-terminated surfaces, HS(CH₂)₁₅COOH and HS(CH₂)₁₀COOH were used]. The adsorption process of thiols to the metal substrate was allowed to take place for a minimum of 6 h at room temperature (RT). The resulting surfaces were rinsed with excess ethanol and dried under a pressurized N₂ flow. Microcontact printing was performed using published procedures.^{34,35}

ACC Precipitation. ACC was deposited by immersing the hydroxyl-terminated template in 25 mM solutions of CaCl₂. The ACC formation took place inside a desiccator containing solid ammonium carbonate as the source of CO₂ at RT for 30 min to 1 h.^{34,36} The resulting ACC on the templates was rinsed with acetone and dried under N₂. The amorphous character of the precipitate was analyzed by Raman spectroscopy (see the Supporting Information, Figure S1). In several experiments, various dopants, such as magnesium ions, dyes, proteins, and peptides, were added to a CaCl₂ solution prior to deposition.^{36,37}

Crystallization. In order to induce recrystallization of ACC, a carboxylic acid-functionalized template was brought in direct contact with ACC. A small amount (~1 mL) of water was placed in between the two substrates to initiate the recrystallization process. The presence of ACC and recrystallized calcite crystals was confirmed by optical and scanning electron microscopy (SEM). The orientations of the crystals were determined by X-ray diffraction and morphological analysis.³⁴

Results and Discussion

We have shown previously that SAMs of hydroxyl-terminated alkanethiols [HS(CH₂)₁₁OH] adsorbed on Au films (Au-OH) induce highly controlled oriented nucleation of calcite crystals from the (104) crystallographic plane.^{34,38} The formation of (104)-oriented calcite occurred when the template was kept in a crystallizing solution for more than 2 h. We have noticed that, prior to nucleating the oriented calcite crystals, the Au-OH templates bear spherulitic particles with diameters of 0.3–1.0 μm (Figure 1a,b). These particles were confirmed by Raman spectroscopy to be composed of ACC (see the Supporting Information, Figure S1). The ability of hydroxyl-terminated SAMs to stabilize ACC without any additives is remarkable and is reminiscent of the stabilizing activity of threonine- and serine-rich proteins

-
- (16) Reddy, M. M.; Nancollas, G. H. *J. Cryst. Growth* **1976**, *35*, 33.
 (17) Raz, S.; Weiner, S.; Addadi, L. *Adv. Mater.* **2000**, *12*, 38.
 (18) Faatz, M.; Gröhn, F.; Wegner, G. *Adv. Mater.* **2004**, *16*, 996.
 (19) Xu, A. M.; Ma, Y. R.; Colfen, H. *J. Mater. Chem.* **2007**, *17*, 415.
 (20) Xu, G.; Yao, N.; Aksay, I. A.; Groves, J. T. *J. Am. Chem. Soc.* **1998**, *120*, 11977.
 (21) Li, M.; Mann, S. *Adv. Funct. Mater.* **2002**, *12*, 773.
 (22) Gunther, C.; Becker, A.; Wolf, G.; Epple, M. *Anorg. Allg. Chem.* **2005**, *631*, 2830.
 (23) Lose, E.; Wilson, R. M.; Seshadri, R.; Meldrum, F. C. *J. Cryst. Growth* **2003**, *254*, 206.
 (24) Ajikumar, P. K.; Wong, L. G.; Subramanyam, G.; Lakshminarayanan, R.; Valiyaveetil, S. *Cryst. Growth Des.* **2005**, *5*, 1129.
 (25) Volkmer, D.; Harms, M.; Gower, L.; Ziegler, A. *Angew. Chem., Int. Ed.* **2005**, *44*, 639.
 (26) Donners, J. J. M.; Heywood, B. R.; Meijer, E. W.; Nolte, R. J. M.; Sommerdijk, N. A. J. M. *Chem.—Eur. J.* **2002**, *8*, 2561.
 (27) Xu, A.-W.; Yu, Q.; Dong, W.-F.; Antonietti, M.; Cölfen, H. *Adv. Mater.* **2005**, *17*, 2217.
 (28) Gower, L. B.; Odom, D. J. *J. Cryst. Growth* **2000**, *210*, 719.
 (29) Olszta, M. J.; Gajjeraman, S.; Kaufman, M.; Gower, L. B. *Chem. Mater.* **2004**, *16*, 2355.
 (30) Cheng, X. G.; Gower, L. B. *Biotechnol. Prog.* **2006**, *22*, 141.
 (31) Lose, E.; Meldrum, F. C. *Chem. Commun.* **2001**, *10*, 901.
 (32) Lose, E.; Park, R. J.; Warren, J.; Meldrum, F. C. *Adv. Funct. Mater.* **2004**, *14*, 1211.
 (33) Lippmann, F. *Sedimentary Carbonate Minerals*; Springer-Verlag: Berlin, 1973.

-
- (34) Aizenberg, J.; Black, A. J.; Whitesides, G. M. *J. Am. Chem. Soc.* **1999**, *121*, 4500.
 (35) Love, J. C.; Estroff, L. A.; Kriebel, J. K.; Nuzzo, R. G.; Whitesides, G. M. *Chem. Rev.* **2005**, *105*, 1103.
 (36) Albeck, S.; Aizenberg, J.; Addadi, L.; Weiner, S. *J. Am. Chem. Soc.* **1993**, *115*, 11691.
 (37) Han, Y.-J.; Aizenberg, J. *J. Am. Chem. Soc.* **2003**, *125*, 4032.
 (38) Aizenberg, J.; Black, A. J.; Whitesides, G. M. *Nature* **1999**, *398*, 495.

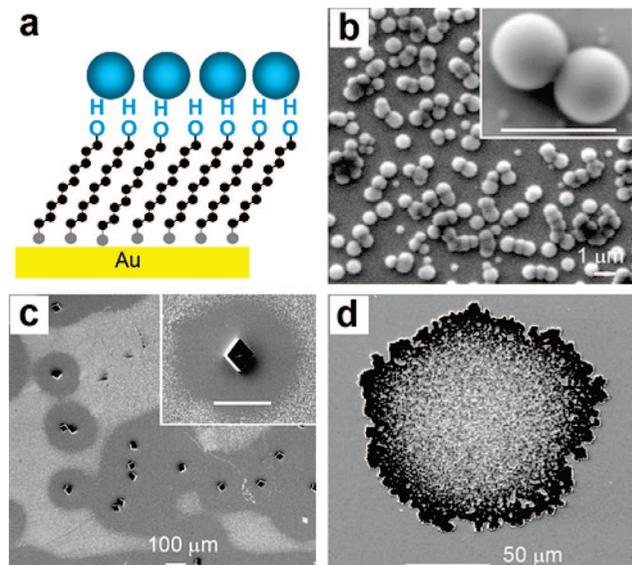


Figure 1. Stabilization of ACC on a hydroxyl-terminated template. (a) Schematic illustration of the ACC formation on a Au-OH SAM. (b) SEM of the ACC spheres removed from the solution after 45 min. Inset: high-magnification image. (c) SEM of the Au-OH template removed from the solution after 1.5 h. Recrystallization of ACC into the (104)-oriented calcite crystals began to occur in the solution. Inset: high-magnification image, showing a calcite crystal nucleated from the (104) plane grown in the ACC background. (d) When exposed to a humid atmosphere, ACC spheres on a Au-OH template flatten, spread, fuse, and form a continuous film that slowly crystallizes.

isolated from biogenic ACC.^{4,13} The exact mechanism of how OH-terminated molecules stabilize ACC in natural and synthetic environments is unknown and requires further investigation.

By systematically removing the substrates at different time intervals from the crystallizing solution, we observed the formation of ACC as well as its transition to oriented calcite crystals. When left in the crystallizing solution, ACC particles slowly transformed into (104)-oriented calcite crystals (Figure 1c). The crystals grew at the expense of the amorphous phase, leaving behind a depletion halo in the consumed ACC film (Figure 1c, inset). When the Au-OH templates bearing spherical ACC deposits were removed from the solution before crystallization and then kept in a dry atmosphere, ACC was stabilized and did not transform into calcite.²² When exposed to a humid environment, ACC particles slowly start to self-dissolve, flatten, spread, fuse, and crystallize into a (104)-oriented calcitic film (Figure 1d).³⁹ If placed in water after being dried, the ACC phase transforms into the (104)-oriented crystals in about 2 h (Figure 1c).

In this work, we explore the ability to govern the recrystallization process, so that instead of the uncontrolled transition of the ACC particles on the Au-OH surface into the (104)-oriented calcite, the crystallization can now be triggered on demand and the growth of crystals in various, highly controlled orientations could be achieved. To realize this goal, we fabricated a secondary SAM template that had a high calcite-nucleating capability. We have reported earlier that carboxylic acid-terminated SAMs supported on gold are very active in inducing the nucleation of calcite.^{14,34,37,40}

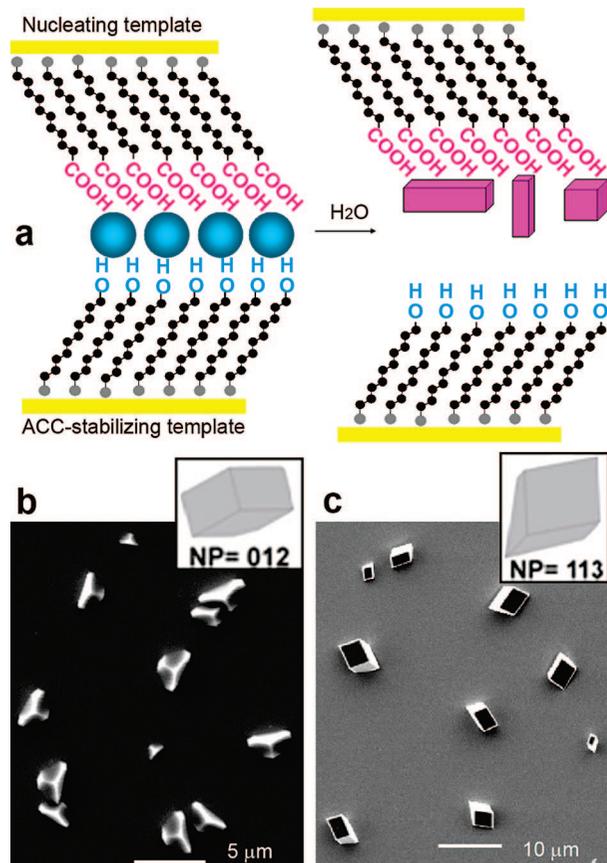


Figure 2. Recrystallization of the ACC stored on the primary Au-OH template when brought in contact with a secondary template functionalized with calcite nucleation sites. (a) Schematic presentation of the process. (b) SEM of the oriented calcite crystals formed on a secondary nucleating template of Au-C₁₅-COOH. Oriented nucleation from the calcite (012) plane induced by the Au-C₁₅-COOH template^{34,40} takes place. The inset shows a computer simulation of the crystal nucleated from the (012) nucleation plane (NP). (c) SEM of the oriented calcite crystals formed on a secondary nucleating template of Au-C₁₀-COOH. Oriented nucleation from the calcite (113) plane induced by the Au-C₁₀-COOH template⁴⁰ takes place. The inset shows a computer simulation of the crystal nucleated from the (113) NP.

Moreover, oriented crystal growth occurs, and the crystals are oriented with the (01*l*) nucleating plane (*l* = 2–5) when grown on the SAM of HS(CH₂)₁₅COOH and with the (113) nucleating plane when grown on the SAM of HS(CH₂)₁₀COOH.⁴⁰ The secondary templates bearing COOH-terminated SAMs (Au-C_{*n*}-COOH) were brought in direct contact with the primary Au-OH template covered with the ACC (Figure 2a). The crystallization was initiated by introducing H₂O to the system at ambient temperature and pressure. Within 15 min of the introduction of a droplet of H₂O, the transformation of ACC to calcite crystals was complete, as observed by optical microscopy and SEM. The crystals grew on the secondary template by consuming the ACC reservoir. The secondary template played a critical role in inducing the recrystallization process by significantly reducing the induction time for nucleation, as well as in controlling the orientation and shapes of the transformed calcite crystals. Calcite crystals nucleated from the (012) plane were formed on the Au-C₁₅-COOH template (Figure 2b), and calcite crystals nucleated from the (113) plane were formed on the Au-C₁₀-COOH template (Figure 2c). When a slow nucleating surface, such as methyl-terminated SAM

(39) Xu, X. R.; Han, J. T.; Cho, K. *Chem. Mater.* **2004**, *16*, 1740.

(40) Han, Y.-J.; Aizenberg, J. *Angew. Chem., Int. Ed.* **2003**, *42*, 3668.

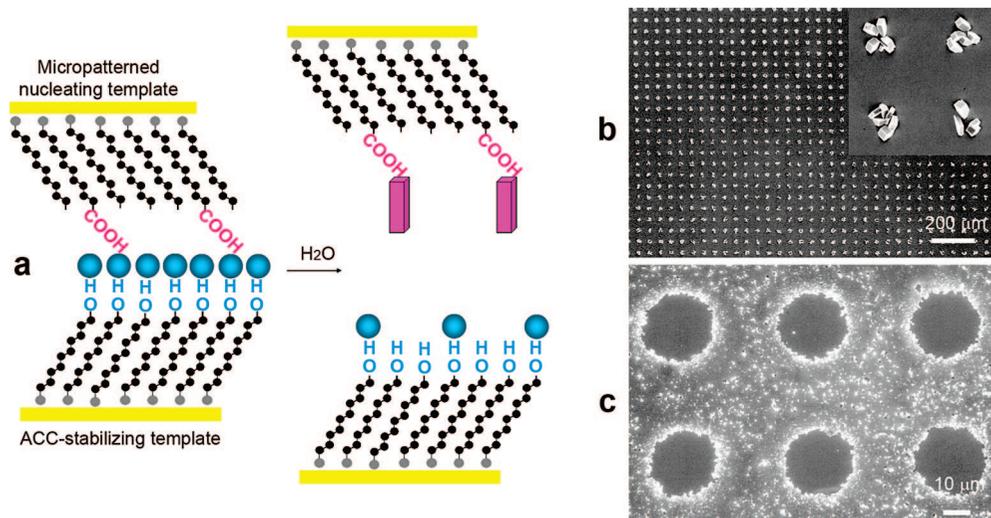


Figure 3. Recrystallization of the stored ACC film into a micropatterned crystalline array upon contacting a secondary template decorated with a micropattern of nucleating sites. (a) Schematic presentation of the process. (b) Highly regular square array of (012)-oriented calcite crystals formed on a secondary template, on which a pattern of 10- μm circles of HS(CH₂)₁₅COOH SAM was formed in the HS(CH₂)₁₁CH₃ background by microcontact printing. (c) Pattern opposite to the one formed on the secondary nucleating template is left on the ACC film.

[HS(CH₂)₁₁CH₃ on Au],³⁸ was placed on top of the ACC particles, no crystallization was observed on the secondary template. Instead, the transformation occurred on the primary OH-terminated surface and the (104)-oriented calcite crystals were formed in 1.5–3 h, as depicted in Figure 1c.

Our results show that, by separating the template for the ACC deposition from the nucleating template, we were able to store the amorphous phase until needed and use it as an ion reservoir for the recrystallization process when the crystallization is desired. It is important to emphasize again that the transformation of ACC to calcite occurs in the absence of any additional calcium and carbonate ions. It is hypothesized that the recrystallization process only requires a very small amount of H₂O to dissolve the very soluble ACC particles within the confined space near the secondary surfaces. The presence of the appropriate functional groups (e.g., carboxylic acid) on the secondary template in near proximity to the dissolving ACC particles is essential for changing the energy landscape in the system; in other words, for concentrating the dissolved ions to reach high supersaturation levels and providing nucleation sites for oriented calcite crystallization. Currently, experiments to convert ACC particles to calcite crystals in the presence of a secondary nucleating template by controlling the humidity level are underway.

In addition to inducing oriented nucleation on demand, we can control the precise location and pattern of crystallization. For example, we used microcontact printing to form various patterns of carboxylic acid-terminated spots in the methyl-terminated background on the secondary template.^{38,41} When such a micropatterned template was brought in contact with the ACC, the crystal growth occurred only at the patterned locations (Figure 3a). For example, Figure 3b shows a square array of oriented calcite crystals formed on a secondary surface. Interestingly, when the substrates were removed from the solution and dried prior to the recrystal-

lization of the residual ACC particles on the OH-terminated surface, a patterned ACC film with the features opposite to those formed on the secondary template remained on the Au-OH surface (Figure 3c). Our strategy makes it possible, therefore, to template both crystalline and amorphous micropatterned structures.

It has also been shown previously that ACC synthetic and biogenic particles can be formed in the presence of dopants such as Mg²⁺ ions and organic molecules (e.g., peptides, polymers).^{17–30} This led us to believe that ACC might be potentially used as a general storage medium for various foreign molecules along with calcium and carbonate ions (Figure 4a). In order to confirm this hypothesis, experiments were carried out to produce several batches of ACC spherulites with varying amounts of dopants incorporated in their structures. Mg²⁺ ions were used as the initial dopant because magnesium ions are often associated with biogenic calcium carbonates and the effect of magnesium on the formation of synthetic ACC has been extensively studied.^{17,23,24} Spherulitic ACC particles with different concentrations of Mg²⁺ ions were synthesized by adding varying concentrations of Mg²⁺ to the calcium chloride solution (Mg/Ca = 0–5). The resulting ACC spherulites formed on the surfaces of Au-OH templates showed spherical morphologies identical to those synthesized in the absence of Mg²⁺ ions. The incorporation of Mg²⁺ ions to the ACC spherulites was qualitatively confirmed by EDAX measurements (see the Supporting Information, Figure S2). The transformation of ACC doped with Mg²⁺ to calcite crystals was performed as described for the undoped case. Calcite crystals formed on the secondary template showed modified morphologies, compared to a regular calcite rhombohedron. The morphological changes were consistent with the modified morphologies reported earlier for calcite crystals grown from solution by the supersaturation methods with Mg²⁺ ions.^{36,37} In particular, the growth of calcite crystals in the *ab* plane was hindered by the presence of Mg²⁺ ions, resulting in the anisotropic elongation of the crystals in the *c*-axis direction (Figure 4b). We have shown that the extent to which the morphological change takes place depends on the

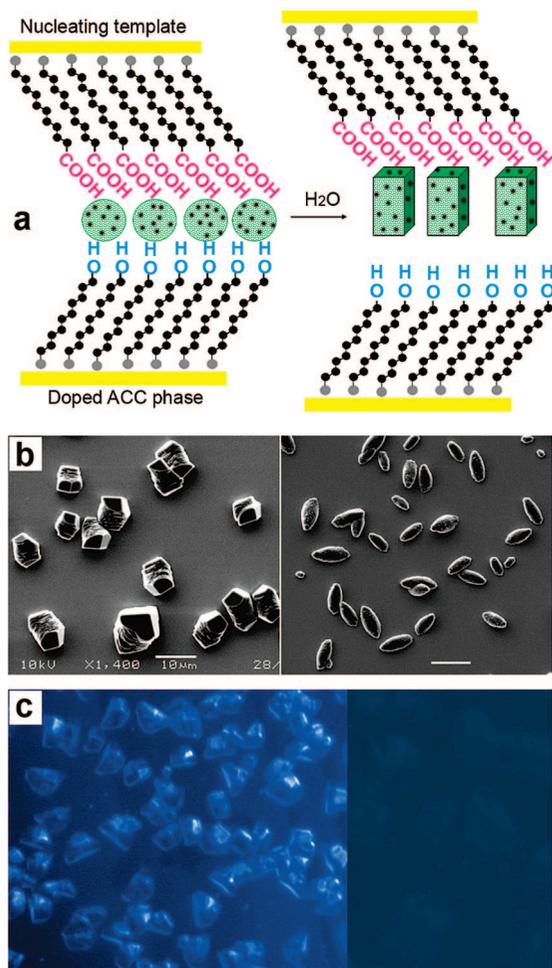


Figure 4. ACC particles can be used as a general storage medium for foreign ions and macromolecules that affect the growth and composition of recrystallized calcite. (a) Schematic presentation of the process. (b) SEM of calcite crystals recrystallized on a Au-C₁₀-COOH template from the ACC phase doped with magnesium ions. Magnesium is incorporated into the crystals and induces a typical morphological modification. The extent to which the crystals are affected depends on the doping level: Mg/Ca = 1 (left); Mg/Ca = 2 (right). (c) Left: Fluorescent light micrograph of calcite crystals recrystallized on a Au-C₁₅-COOH template from the ACC phase doped with a fluorescent dye. The dye is clearly incorporated into the crystals. Right: Control experiment with no dye.

concentration of Mg²⁺ ions in the solution.³⁷ Similarly, the newly transformed calcite crystals on the HS(CH₂)₁₀COOH-functionalized secondary template were affected by Mg²⁺ ions in a varying degree depending on the concentration of magnesium ions incorporated within the ACC spherulites (Figure 4b). Interestingly, when the incorporation of Mg²⁺ ions into the ACC particles was greater than ~10 mol %, only ultrastable ACC particles formed, which did not transform to calcite crystals even when the secondary surface was introduced. This may be a pathway for biological species to control the formation of soluble (temporary) and permanent biogenic ACC structures. Currently, we are determining the exact concentration of magnesium ions in stable ACC particles using a high-resolution secondary ion spectrometer (nanoSIMS).

We have also studied the ability to store various organic molecules in ACC and their incorporation into the recrystallized calcite. For example, L-aspartic acid (L-Asp) and fluorescent dyes were chosen as the dopants. Similar to the

results observed for Mg²⁺-doped ACC, various concentrations of L-Asp or dyes can be introduced to synthetic ACC. In the vast majority of organics-doped ACC, the transformation to calcite by contacting the secondary nucleating template resulted in the formation of organics-doped calcite crystals (Figure 4c). The fluorescence did not disappear after partial dissolution of the crystals, confirming that in addition to the surface-bound molecules the dopant was incorporated into the bulk of the crystals. In some cases, the organic molecules were excluded from the crystalline phase and were adsorbed on the surfaces of the crystals.¹⁴

These results clearly demonstrate that inorganic or organic dopants can be stored in the ACC spherulites in various concentrations. These doped ACC spherulites can then function as reservoirs for ions other than calcium and carbonate, which would affect the crystallizing behavior of the resulting crystals and be incorporated into their structure. We can speculate that a similar phenomenon might be relevant to naturally occurring ACC in biological species. It is conceivable that, during the formation of biogenic ACC, organisms may deposit additional metal ions and/or organic molecules within the phase. Then, when a need arises to construct crystalline calcium carbonates with specific morphology, orientation, and strength, the incorporated molecules codissolve along with calcium carbonates from the composite ACC and contribute to the formation of crystalline material by controlling their morphologies, sizes, shapes, impurity content, and defect distribution.

In conclusion, a successful synthesis of ACC with and without additives was achieved by using a hydroxyl-terminated SAM as the template for calcium carbonate precipitation. The ACC can be stabilized in a dry atmosphere and utilized as a precursor phase for the recrystallization into calcite. Crystallization can be triggered on command when desired by introducing a secondary template engineered with appropriate active functional groups to induce nucleation in an aqueous environment. Foreign molecules and ions can be doped into synthetic ACC particles and further participate in the recrystallization process and accumulate in the newly formed crystals. This approach makes it possible to control the timing of the recrystallization process, the orientation of the crystals, their doping, morphology, and micro/nanopattern of crystallization. The advantage of this system is that ACC can be indefinitely used as a storage of ions, and the highly controlled crystallization process is facilitated by an appropriate nucleating template, conceivably similar to the mechanism of amorphous-to-crystalline transition occurring in nature.

Acknowledgment. We thank Dongbo Wang of Virginia Tech for the Raman spectroscopy measurement of ACC and calcite. This work was performed in part under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under Contract DE-AC52-07NA27344.

Supporting Information Available: Raman spectroscopy measurements of ACC and EDAX measurements of magnesium-doped ACC. This material is available free of charge via the Internet at <http://pubs.acs.org>.

CM702032V